

Non Destructive Testing
Building Materials
Aggregates
Concrete
Soils

JOHN H. ROBINSON TESTING, INC.

(A Subsidiary of Urban Engineers, Inc.)
1319 Sassafras Street, Erie, PA 16501
LABORATORY PHONE (814) 454-0195
FAX (814) 453-2020

Sub-Surface Investigating
Field Testing & Inspection
Soil Mechanics
Soil Borings
Reports

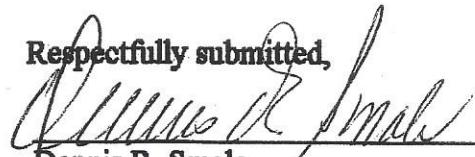
Date: February 2, 2004
Client: Gutters, Insulation & More
4002 Main Street
Erie, PA. 16511
Attn: Mr. Bill Szabo
Re: "R" Value Evaluation
Concrete Block: air-krete® foam-filled
Lab Ref.: Z-04-006
Received: 01-16-2004
Examined with the following results:

Three (3) air-krete® foam-filled concrete block specimens were submitted to testing procedures as outlined in ASTM C-518 to determine their "R" value. The block were first conditioned to ambient laboratory temperature and relative humidity (70 degrees F & 37% RH) for 24 hours prior to performing the test procedure. The block were evaluated in both the 10" direction and the 8" direction to arrive at "R" values indicative of the two primary types of residential masonry units currently being retro-fitted with the insulation product here evaluated.

<u>Masonry Unit Designation</u>	<u>"R" Value</u>
2-core, 10" regular concrete block	25
2-core, 8" regular concrete block	18

It must be noted that these derived values do not take into account any "dynamic" influences on the actual building system as constructed. That is to say that the effect of wind, moisture, leakage at mortar joints or expansion joints, presence of waterproofing materials on one or both sides of the block construction, severe humidity differences across the masonry construction or combinations of any of these driving forces have not been taken into account in this evaluation. These influences, if they are to be determined, should be evaluated on a "fully constructed" wall assembly as noted in ASTM C-976 *Test Method for Thermal Performance of Building Assemblies by Means of a Calibrated Hot Box*.

Respectfully submitted,


Dennis R. Smale,
Laboratory Superintendent